Food Science of Animal Resources

Food Sci. Anim. Resour. 2025 May 45(3):688~710 DOI https://doi.org/10.5851/kosfa.2025.e13

REVIEW

Scaffold Biomaterials in the Development of Cultured Meat: A Review

Su-Min Park[†], Ji-Hwan Ryoo[†], Hyuk Cheol Kwon[†], and Sung Gu Han^{*}

Department of Food Science and Biotechnology of Animal Resources, Konkuk University, Seoul 05029, Korea

Abstract Cultured meat offers a sustainable and ethical solution to the environmental and food security challenges associated with conventional meat production. In cultured meat production, scaffolds play an important role as structural and biochemical supports for cell adhesion, proliferation, and differentiation. The selection of biomaterials directly influences cellular processes and consequently shape the texture, flavor, and overall quality of the cultivated meat. This review provides a comprehensive overview of biomaterials employed in cultured meat scaffolds, encompassing sources such as animals, plants, algae, and microorganisms. The strengths and limitations of each biomaterial type are critically analyzed to guide scaffold fabrication strategies. Furthermore, potential applications are explored to address the constraints of individual biomaterials. Animalderived biomaterials improve cell adhesion and biocompatibility by imitating extracellular substrates but are limited by high cost and low mechanical strength. Although plantderived biomaterials are cost-effective and biodegradable, their mechanical strength and biocompatibility should be enhanced through chemical modification or combination with other biomaterials. Algae-derived biomaterials provide gelling properties but lack cellbinding sites and mechanical stability. Microbial-derived biomaterials provide high mechanical strength, while the lack of nutritional value and cell-binding sites limits their application in scaffold fabrication. Each biomaterial possesses unique properties, presenting both advantages and disadvantages. By leveraging their strengths, individual biomaterials can serve as effective sources for scaffold construction. An understanding their strengths, limitations, and suitability is crucial for designing and fabricating optimal scaffolds, ultimately enabling the successful production of cultured meat.

Keywords cultured meat, scaffold, biomaterial, cell differentiation, cell proliferation

Introduction

Meat is a major animal-derived protein resource, containing all essential amino acids for human nutrition (Li et al., 2022b; Zheng et al., 2022a). However, conventional meat production processes such as livestock farming and feed production release significant amounts of greenhouse gases, consume vast quantities of land and water resources, and contribute to soil erosion and water pollution (Bomkamp et al., 2022; Chen et al.,

© KoSFA. This is an open access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (http://creativecommons.org/licences/by-nc/3.0) which permits unrestricted non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

OPEN ACCESS

'SAR

1978

Received	November 19, 2024
Revised	January 23, 2025
Accepted	February 18, 2025

*Corresponding author : Sung Gu Han Department of Food Science and Biotechnology of Animal Resources, Konkuk University, Seoul 05029, Korea Tel: +82-2-450-0526 Fax: +82-2-4556-1044 E-mail: hansg@konkuk.ac.kr

*ORCID

Su-Min Park https://orcid.org/0009-0003-9984-8078 Ji-Hwan Ryoo https://orcid.org/0009-0003-5349-5254 Hyuk Cheol Kwon https://orcid.org/0000-0001-6234-2530 Sung Gu Han https://orcid.org/0000-0002-1485-861X

⁺ These authors contributed equally to this work.

2023a). Recently, the demand for meat has increased owing to urbanization and economic development (Lu et al., 2022). In addition, animal welfare issues such as large-scale intensive livestock farming have raised concerns regarding the sustainability of meat production techniques (Bomkamp et al., 2022). For example, agriculture utilizes 92% of global freshwater resources yearly, with 29% used for animal farming (Gerbens-Leenes et al., 2013). In addition, annual greenhouse gas emissions from meat production range from 4.6 to 7.1 billion tons, constituting 15%–24% of global emissions (Fiala, 2008). Therefore, the development of transformative technologies for sustainable meat production is imperative.

Cellular agriculture, which involves the production of agricultural products using cell culture techniques, is receiving attention as an innovative technology because of its potential to address food security and sustainability (Wang et al., 2024e). Cultured meat, a major product of cellular agriculture, was reported to decrease environmental impacts regarding land and water use, compared to conventional meat (Bhat et al., 2015; Djisalov et al., 2021; Tuomisto and Teixeira de Mattos, 2011). Cultured meat offers ethical advantages by minimizing animal use while producing large quantities of muscle tissue. It also contributes to environmental sustainability by reducing greenhouse gas emissions, particularly nitrous oxide released from animal waste (Chriki et al., 2022; Djisalov et al., 2021). Additionally, the risk of *Salmonella* and *Listeria* associated with conventional meat can be avoided without the use of antibiotics (Post et al., 2020).

The production of cultured meat through cellular agriculture technology is based on four fundamental components: cells, cultured media, scaffolds, and biological processes (Murugan et al., 2024; Santos et al., 2023). Scaffolds play an important role in imitating the three-dimensional (3D) structure of conventional meat. Scaffolds can be fabricated from various biomaterials through techniques such as freeze-drying, 3D bioprinting, electrospinning, and electrospray, supporting an integrated network for cell attachment, proliferation, and differentiation (Bezjak et al., 2024; Kumar et al., 2023; Levi et al., 2022; Wei et al., 2023). The structural network of scaffolds depends on the selected biomaterials and fabrication techniques, and thus affects the physicochemical and mechanical properties of cultured meat (Kumar et al., 2023; Levi et al., 2022; Santos et al., 2024). In addition, as scaffolds are directly ingested with cultured meat, it is crucial to ensure both their nutritional value and safety for human consumption (Guo et al., 2024; Wang et al., 2024b).

Recently, various studies have been conducted to evaluate the physicochemical and biological properties of scaffolds using edible biomaterials for cultured meat production (Lee et al., 2024a; Lee et al., 2024b; Wang et al., 2024a; Wang et al., 2024c). The choice of scaffold materials should be guided by the need to closely replicate the optimal properties of the target tissue, while also providing the necessary support for cell adhesion, proliferation, and differentiation (Samandari et al., 2023; Xiang et al., 2022). In fact, although scaffold biomaterials have been predominantly discussed in the field of tissue engineering, there is still a lack of knowledge regarding the optimal scaffold biomaterials for producing cultured meat. Therefore, the primary objective of this review was to provide a comprehensive understanding of the biomaterials used in cultured meat scaffolds, with the goal of informing the selection of optimal materials for efficient cultured meat production.

Animal-Derived Biomaterials

Animal-derived biomaterials offer great potential as scaffold sources due to their edible and biodegradable properties (Wang et al., 2023a). These are primarily categorized into polysaccharides (chitosan), proteins (collagen, gelatin, and fibrin), and polynucleotides (Seah et al., 2022). These biomaterials provide a native environment that support cell growth and differentiation into tissues in cultured meat (Reiss et al., 2021). In particular, the components of the extracellular matrix (ECM) are ideal biomaterials because of their similarity to the texture and structure of conventional meat (Tarafdar et al.,

2021). However, quality control challenges, such as ensuring safety against pathogens and maintaining consistent properties, along with high production costs, prevent the widespread use of animal-derived biomaterials. Importantly, the excessive use of animal ingredients may compromise the fundamental objectives of cultured meat production, like animal welfare (Ahmad et al., 2021; Lee et al., 2024a). Table 1 summarizes the characteristics of animal-derived biomaterials. Chitosan offers biocompatibility and biodegradability but requires additional biomaterials to improve structural integrity. Collagen provides cell adhesion sites and biocompatibility but lacks mechanical strength. Gelatin supports cell adhesion and growth but has limitations in gel formation owing to its low melting point. Fibrin offers biocompatibility but is limited by its high cost. Therefore, animal-derived biomaterials should be combined with other materials to achieve optimal scaffold properties for cultured meat.

Chitosan

Chitosan, an abundant natural polymeric polysaccharide, is typically derived from waste products of the shellfish industry and can also be produced from non-animal sources, such as fungi (Wang et al., 2024d; Xie et al., 2024). Chitosan is a foodgrade biomaterial that is generally recognized as safe (GRAS; Zernov et al., 2022). Chitosan contains abundant amine (-NH₂) and hydroxyl (-OH) groups able to crosslink with cells and share structural similarities with glycosaminoglycans, a component of the ECM (Li et al., 2022b; Wu et al., 2024). Accordingly, the structure of chitosan provides a microenvironment for cell adhesion and proliferation, contributing to desirable properties for scaffold fabrication (Chen et al., 2010; Cooper et al., 2010). However, chitosan must be combined with other biomaterials to improve its structural integrity because of its weak mechanical properties when used as a standalone material (UI-Islam et al., 2024). A previous study incorporated 2% chitosan with 2% sodium alginate, 0.5% collagen, and 0.5% gelatin (2:2:1:1 ratio) through electrostatic interactions to improve mechanical properties of the scaffold (Li et al., 2022b). This scaffold exhibited laminar porous structures with interconnected

Туре	Biomaterial	Strength	Limitation	Reference
Polysaccharide	Chitosan	Food-grade biomaterials, contain cross- linking functional groups, resemble glycosaminoglycans, provide a microenvironment for cell adhesion and proliferation	Weak mechanical properties, low structure integrity	Chen et al. (2010); Cooper et al. (2010); Li et al. (2022b); Ul-Islam et al. (2024); Wu et al. (2024); Zernov et al. (2022)
Protein	Collagen	Contain Arg-Gly-Asp (RGD) motif, repetitive receptor-recognition motifs, promote cell adhesion and cell interaction, high biocompatibility, low immunogenicity, biodegradability, edible	High cost, low mechanical strength	Chen et al. (2024a); Davidenko et al. (2015); Li et al. (2022b); Wang et al. (2024d); Zernov et al. (2022)
	Gelatin	Contain RGD sequences, support cell adhesion and growth, safety, biocompatible, biodegradable, mechanical support, contain intrinsic integrin-binding domains	Low melting point, low shape stability, poor mechanical strength, low elasticity	Chen et al. (2023b); Kong et al. (2022); Li et al. (2022a); Rao et al. (2023); Xing et al. (2014)
	Fibrin	Contain As, Bβ, and γ peptide chains, biocompatibility, bind proteins and growth factors	High production cost, weak mechanical properties	Contessi Negrini et al. (2020); Haugh et al. (2012); Rojas-Murillo et al. (2022); Tan et al. (2021)

Table 1. Properties of animal-derived biomaterials for manufacturing scaffolds

fibrils between the layers (Li et al., 2022b). This enhanced the compressive strength and promoted the proliferation and differentiation of porcine skeletal muscle satellite cells. In addition, microcarriers supplemented with 2% chitosan and 1% collagen (9:1 ratio) significantly enhanced viability and proliferation of primary rabbit smooth muscle cells, sheep fibroblasts, and bovine umbilical cord mesenchymal stem cells (Zernov et al., 2022). Collectively, chitosan can be employed in scaffold fabrication to enhance mechanical strength and biocompatibility when combined with other biomaterials.

Collagen

Collagen is the primary component of the muscle connective tissue and is extracted from the ECM (Zheng et al., 2022a). Collagen contains abundant Arg-Gly-Asp (RGD) motifs and repetitive receptor-recognition motifs that promote cell adhesion and cell interaction (Chen et al., 2024a; Davidenko et al., 2015; Zernov et al., 2022). Furthermore, collagen has inherent characteristics, such as high biocompatibility, low immunogenicity, and biodegradability, which make it suitable for use as an edible scaffold material (Li et al., 2022b; Wang et al., 2024d). However, the high cost and low mechanical strength of collagen remain challenges for its application as a biomaterial for scaffolds (Li et al., 2022b; Zernov et al., 2022). To address these limitations, a previous study developed a scaffold fabricated with 1% collagen, 5% proanthocyanidins, and 5% dialdehyde chitosan in a ratio of 88:4:8 through electrostatic interactions and Schiff base reactions (Wang et al., 2024d). The collagen-proanthocyanidins-dialdehyde chitosan scaffold exhibited superior mechanical (microstructure and compression strength), physical (porosity, swelling ratio, and degradation ratio), and biological (adhesion, proliferation, differentiation of primary skeletal muscle myoblasts) properties, compared to pure collagen scaffold (Wang et al., 2024d). In addition, a prior study fabricated an aligned porous scaffold crosslinked with 4% collagen and 30 U/g transglutaminase through ice-templated directional freeze-drying to improve the cost and structure of cultured meat (Chen et al., 2024a). The cultivation of porcine skeletal muscle satellite cells on this aligned porous scaffold improved mechanical strength (microstructure, hardness, chewiness, and resilience), proliferation (live cell fluorescence), and differentiation (F-actin fluorescence, myogenin, and myosin; Chen et al., 2024a). In scaffold fabrication, collagen can become a suitable biomaterial through the establishment of methods to enhance mechanical strength and reduce costs in combination with various biomaterials.

Gelatin

Gelatin is a product of collagen hydrolysis containing RGD sequences that support cell adhesion and growth (Chen et al., 2023b; Rao et al., 2023). The U.S. Food and Drug Administration (FDA) considers gelatin to be safe, biocompatible, and biodegradable (Li et al., 2022a; Rao et al., 2023). Gelatin has been employed as a mechanical support for cell attachment due to its intrinsic integrin-binding domains (Kong et al., 2022). However, since gelatin has a relatively low melting point of approximately 28°C–30°C, a gelatin hydrogel formed through non-covalent associations below 30°C–35°C is easily destroyed at physiological temperatures of 37°C (Xing et al., 2014). Therefore, the gelatin hydrogel possesses low shape stability, poor mechanical strength, and low elasticity, limiting its application in cultured meat production. These limitations can be addressed by inducing covalent crosslinking to enhance mechanical stability and by employing as a coating material to improve biocompatibility. According to a previous study, various concentrations of gelatin (0%, 0.5%, and 1%) were coated to scaffold fabricated with 5% soy protein and 2% agarose in a 1:1 ratio (Hong et al., 2024). The 1% gelatin-coated scaffold increased water absorption rate, mechanical strength, cell attachment, and lipid accumulation in adipose tissue-derived stem cells compared to the non-coated scaffold (Hong et al., 2024). Additionally, textured vegetable protein was coated with 6% gelatin and agar at ratios of 4:0, 4:0, 5, 4:1, and 4:3 (Lee et al., 2022). The gelatin and agar coating at a ratio of 4:1

demonstrated optimal hydrogel stiffness and stability comparable to muscle and enhancing cell attachment, proliferation, and mechanical strength (Lee et al., 2022). Considering these previous studies, the enhancement of mechanical properties in gelatin enables its application as a biomaterial in cultured meat production.

Fibrin

Fibrin is a byproduct of fibrinogen, which is composed of As, B β , and γ peptide chains (Tan et al., 2021). Fibrin is a suitable biomaterial for scaffolds owing to its biocompatibility and ability to bind proteins and growth factors (Rojas-Murillo et al., 2022). However, fibrin produced from human thrombin and fibrinogen has a high production cost (Contessi Negrini et al., 2020). Furthermore, the weak mechanical properties of fibrin hydrogel due to its hydrated nature (i.e. the low protein to water ratio) limits its use in cultured meat application (Haugh et al., 2012). To overcome these limitations, a study developed hydrogel scaffolds combined with fibrin and konjac glucomannan at a ratio of 3:2 (Tang et al., 2024). The 1.2% fibrin and 0.8% konjac glucomannan hydrogels induced glycosylation through hydrogen-bond interactions and possesed suitable degradation rate, water holding capacity, textural properties, and biocompatibility for cultured meat production (Tang et al., 2024). Moreover, a fibrin hydrogel mixed with 10 mg/mL fibrinogen and 5 U/mL thrombin was fabricated in a 15 mm long section of silicone tube tissue mold, cultivating piscine satellite cells at a concentration of 6.0×10^6 cells/mL for cultured fish meat production (Lou et al., 2024). This fibrin matrix exhibited superior biocompatibility (cell viability, proliferation, differentiation, and alignment) along with textural and nutritional similarity to natural fish fillets (Lou et al., 2024). These reports indicate that fibrin, while promising for cultured meat when combined with other biomaterials or structurally aligned, requires cost-effective separation and extraction methods for widespread adoption.

Plant-Derived Biomaterials

Plant-derived biomaterials are an attractive option for scaffold fabrication in cultured meat, given that the primary purpose of cultured meat is to reduce the reliance on animal-derived materials (Kim et al., 2024). Also, the fibrous structure of plant-derived biomaterials closely resembles that of conventional meat, making them well-suited for use as scaffolds (Zheng et al., 2022b). Plant-derived biomaterials are classified into polysaccharides and proteins, offering technical and economic advantages such as high nutritional value, biocompatibility, consumer acceptance, and low cost (Ben-Arye and Levenberg, 2019; Ng and Kurisawa, 2021). However, the limited cell attachment of these biomaterials has driven recent research efforts towards developing plant-based scaffolds through the utilization of various scaffolding technologies (Levi et al., 2022; Rao et al., 2023). Table 2 presents the properties of the plant-derived biomaterials in the scaffolds. Polysaccharides such as cellulose, starch, and glucomannan offer biocompatibility, biodegradability, and low cost, making them suitable for cultured meat scaffolds. Proteins, including soy protein, pea protein, zein, and glutenin, enhance cell adhesion, proliferation, and differentiation and have high nutritional value. Decellularized plant-derived materials provide structural support and vascular systems as scaffolds for cultured meat.

Polysaccharides

Cellulose

Cellulose, a natural polymer found in plant cell walls, is composed of D-glucose units linked by β -1,4 glycosidic bonds (He et al., 2021). Cellulose has been widely used in the food and pharmaceutical industries because of its biocompatibility, non-

Туре	Biomaterial	Strength	Limitation	Reference
Polysaccharide	Cellulose	Biocompatibility, non-toxic, eco- friendliness, supports cell proliferation and differentiation	Non-specific protein adsorption, limiting cell adhesion	Courtenay et al. (2017); Klemm et al. (2005); Siró and Plackett (2010)
	Starch	Biodegradability, high availability, low cost, non-toxic	Low mechanical strength, high hydrophilicity	Apriyanto et al. (2022); Buléon et al. (1998); Torres et al. (2013)
	Glucomannan	Excellent gelling and water- holding properties	Lack of hydrophobicity and viscosity, low thermal stability and mechanical strength	Ran and Yang (2022); Ran et al. (2022); Ye et al. (2021); Zhuang et al. (2024)
Protein	Soy protein	High nutritional value, food safety, low cost	Low mechanical properties, insufficient water-resistance	Chien and Shah (2012); Milani and Tirgarian (2020); Mohammadian and Madadlou (2018); Sui et al. (2021); Tian et al. (2018)
	Pea protein	High nutritional content, low allergenicity, availability, affordability, low cost	Low solubility, high denaturation temperature	Başyiğit et al. (2024); Estevinho and Rocha (2018); Li et al. (2020); Shanthakumar et al. (2022); Stone et al. (2015)
	Zein	Biocompatibility, biodegradability, amphiphilicity, self-assembly	Hydrophobicity and deficiency of essential amino acids	Falsafi et al. (2023); Giteru et al. (2021); Wang et al. (2022); Zhang et al. (2023)
	Glutenin	High nutritional value, low cost, biocompatibility	Limited processability, low solubility	Xu et al. (2014); Yao et al. (2024)
Decellularized	Parsley	Supports cell proliferation and	Different structural and	Chen et al. (2024b);
plant-derived materials	Apple	differentiation, provides a vascular system for supplying	functional properties dependent on the type	Contessi Negrini et al. (2020); Jones et al. (2023);
	Banana leaf	oxygen and nutrients, low cost,	of plant	Murugan et al. (2024);
	Spinach	- edibility		Thyden et al. (2022)
	Celery	_		
	Mushroom	_		

toxicity, and eco-friendliness (Klemm et al., 2005; Siró and Plackett, 2010). However, the hydrophilicity of natural cellulose due to its hydroxyl groups reduces non-specific protein adsorption, thereby limiting cell adhesion (Courtenay et al., 2017). To overcome these limitations, cellulose derivatives are frequently employed in scaffold fabrication. These derivatives, including cellulose acetate and carboxymethylcellulose, are modified by substituting the hydroxyl groups of natural cellulose with acetyl and carboxyl groups (Park et al., 2021; Santos et al., 2024). Cellulose nanofiber scaffolds in random or aligned forms have been fabricated using a 12% cellulose acetate solution via electrospinning. The random cellulose acetate nanofibers with a porous structure have supported suitable adhesion and differentiation of C2C12 and H9c2 myoblasts, demonstrating their potential application for cultured chicken meat (Santos et al., 2024). In addition, a polysaccharide film platform has been developed to produce cost-effective cultured meat via the replacement of animal-derived serum with C-phycocyanin extracted from blue algae. The polysaccharide films were fabricated into multilayer structure composed of carboxymethylcellulose and chitosan through electrostatic interaction-based layer-by-layer assembly process. These film platforms provided a porous

structure for effective incorporation and release of C-phycocyanin, promoted the proliferation of C2C12 cells, and achieved a 4-fold improvement (Park et al., 2021). Collectively, cellulose derivatives, synthesized by modifying natural cellulose through hydroxyl group substitution, can serve as scaffold biomaterials to enhance cell adhesion and proliferation.

Starch

Starch is a biodegradable carbohydrate polymer that is mainly found in corn, wheat, tapioca, rice, and potatoes (Buléon et al., 1998). Owing to its high availability, low cost, nontoxicity, and biodegradability, starch has been widely applied in various industries, including the food industry (Apriyanto et al., 2022). Since the low mechanical strength and high hydrophilicity of starch limit its application as a biomaterial for scaffold fabrication, various studies have been conducted to address these challenges (Torres et al., 2013). Indeed, starch-based scaffolds were developed using 3D printing techniques with 5 g of starch gel combined with 0–0.1 g of calcium carbonate and glucono delta lactone in a 1:2 ratio (Wang et al., 2024a). The addition of calcium carbonate and glucono delta lactone improved mechanical (compression modulus), structural (microstructure, pore size), physical (swelling ratio, digestibility, and water stability), and biological (proliferation and differentiation of C2C12 myoblasts) properties of starch-based scaffolds (Wang et al., 2024a). Additionally, a previous study developed a 3D bioprinting bioink by incorporating 1% and 5% starch nanoparticles into hydrogels composed of 15% gelatin and 1% sodium alginate (Niu et al., 2024). The addition of 1% starch nanoparticles to the gelatin-based hydrogels reduced the viscosity and shear stress of the bioink and increased the proliferation and differentiation of piscine satellite cells, thereby enhancing 3D printability and biocompatibility (Niu et al., 2024). Collectively, starch can be efficiently utilized through either combination with other biomaterials or structural modification into nanoparticles (Lu and Tian, 2021; Niu et al., 2024).

Glucomannan

Glucomannan is a polysaccharide in the mannan family that is commonly found in softwood, roots, tubers, and plant bulbs (Alonso-Sande et al., 2009). Among the various types of glucomannans, the most utilized form is konjac glucomannan, which is extracted from *Amorphophallus konjac* tubers (Xiao et al., 2000a; Xiao et al., 2000b). Konjac glucomannan has been extensively utilized in food and tissue engineering industries owing to its gelling and water holding properties (Ran and Yang, 2022; Ran et al., 2022; Ye et al., 2021). Nevertheless, pure konjac glucomannan exhibits limitations, including low hydrophobicity, viscosity, thermal stability, and mechanical strength (Zhuang et al., 2024). To mitigate these limitations, previous studies have investigated the fabrication of hydrogels by constructing composites of konjac glucomannan with biomaterials such as fibrin or k-carrageenan (Gu et al., 2024; Tang et al., 2024). Konjac glucomannan-based hydrogel composites exhibited enhanced mechanical (hardness and chewiness), physical (viscoelasticity, degradability, and water holding capacity), and biological (cell proliferation and differentiation) properties (Gu et al., 2024; Tang et al., 2024). Therefore, the incorporation of konjac glucomannan with other biomaterials can be an efficient strategy for scaffold fabrication in cultured meat production.

Proteins

Soy protein

Soy protein is a popular alternative to animal-derived proteins because of its high nutritional value, reliable food safety, and low cost (Chien and Shah, 2012; Mohammadian and Madadlou, 2018; Sui et al., 2021). However, low mechanical properties and insufficient water resistance must be addressed to effectively utilize soy protein as a scaffold material (Milani

and Tirgarian, 2020; Tian et al., 2018). For this, a previous study developed aligned porous scaffolds incorporated with 5% soy protein amyloid fibrils and glycerin at ratios of 70:30, 60:40, 50:50, and 40:60 through the unidirectional freeze casting method (Shan et al., 2024). The increase of glycerin content in soy protein-based scaffolds resulted in the formation of smaller and more regular pores, and this reduction in porosity enhanced water resistance and mechanical strength (Shan et al., 2024). In another study, scaffolds composed of 5% soybean protein isolate, 0.5% soybean dietary fiber, and 5% glycerol were crosslinked with both 5.5% transglutaminase and 5.8% calcium chloride (Fang et al., 2024). These scaffolds increased mechanical strength (compression modulus), water resistance (degradation ratio), and biocompatibility (cell viability) compared to those fabricated using transglutaminase or calcium chloride. It seems that the enhancement of water resistance and mechanical strength through the incorporation of other biomaterials is essential for utilizing soy protein as a scaffold biomaterial.

Pea protein

Pea protein is an attractive biomaterial characterized by its high nutritional content, low allergenicity, availability, affordability, and low cost (Li et al., 2020; Stone et al., 2015). Due to these functional properties, pea protein is extensively utilized as a promising ingredient in the food industry (Shanthakumar et al., 2022). Moreover, recent studies have expanded the application of pea protein as a biomaterial for scaffold fabrication in cultured meat production (David et al., 2024; Ianovici et al., 2022). However, the low solubility and high denaturation temperature of pea protein due to a broad range of the isoelectric point from pH 4 to 6 limit its gelling properties for scaffold fabrication (Başyiğit et al., 2024; Estevinho and Rocha, 2018). To address this limitation, a previous study fabricated mold-based scaffolds incorporating 15% pea protein isolate at pH 2 and 7 (David et al., 2024). Pea protein isolates at both pH 2 and 7, combined with 2% alginate, effectively induced gelation in polydimethylsiloxane molds through crosslinking with calcium chloride. Although there were no differences in the physical properties (porosity, connectivity, morphology, and liquid absorption) of scaffolds between pH 2 and 7, the scaffolds at pH 7 exhibited higher proliferation and differentiation of bovine satellite cells compared to those at pH 2 (David et al., 2024). Additionally, 1% pea protein isolates and 1% alginate were mixed in 1:1 ratio to fabricate mold-based scaffold (Ianovici et al., 2022). Pea protein isolates-alginate scaffolds enhanced the mechanical (Young's modulus), physical (porosity, degradability, and liquid uptake), and biological (proliferation and differentiation of bovine satellite cells) properties compared to single alginate scaffolds (Ianovici et al., 2022). Taken together, despite its limitations in solubility and denaturation, pea protein can be utilized for cultured meat scaffold fabrication through optimization of pH and incorporation with alginate, resulting in scaffolds that support cell proliferation and differentiation.

Zein protein

Zein, as a GRAS, is a prolamin protein produced from corn grains via a wet milling process (Falsafi et al., 2023). The biocompatibility, biodegradability, amphiphilicity, and self-assembly of zein can be ideal biomaterials for scaffold fabrication in cultured meat production (Wang et al., 2022). The high percentage of sulfur-containing amino acids in zein leads to hydrophobicity and a deficiency in essential amino acids, thereby restricting its applications (Giteru et al., 2021; Zhang et al., 2023). A prior study injected a 1% hydrophilic sodium alginate solution into a coagulation bath containing 30% zein and 5% calcium chloride solution through a wet-spinning technique to fabricate zein-alginate fiber (Jeong et al., 2024). Zein-coated alginate fibers exhibited higher tensile stress and elastic modulus than alginate fibers. Furthermore, zein-alginate fibers subjected to a 75% strain enhanced alignment and myogenesis during the cultivation of C2C12 and bovine satellite cells

(Jeong et al., 2024). In another study, zein short-stranded fibers, generated from 28% zein solutions by means of electrospinning and ultrasonication, were integrated into RGD-functionalized alginate hydrogels (Melzener et al., 2023). The addition of 0.1% zein fibers into 1.8% alginate hydrogels improved biomaterial degradation, cellular compaction, metabolic activity, and protein productivity (Melzener et al., 2023). Considering these characteristics of zein in scaffold fabrication, hydrophobic zein can be effectively utilized when incorporated with hydrophilic biomaterials.

Glutenin

Glutenin, which consists of gliadin and glutenin, is one of the two main components of wheat gluten. Glutenin is composed of aggregated proteins characterized by interchain disulfide bonds (Abedi and Pourmohammadi, 2021; Wieser, 2007). Glutenin is regarded as a promising biomaterial for scaffold fabrication due to its high nutritional value, cost-effectiveness, and biocompatibility (Yao et al., 2024). Despite these advantages, the highly crosslinked molecular structure of pure glutenin significantly restricts its processability and solubility (Xu et al., 2014). To address this issue, a previous study engineered porous and fibrous glutenin scaffolds. This was achieved by acidifying a 5% glutenin solution to pH 3 and subsequently modifying its secondary structure via water annealing (Xiang et al., 2022). These scaffolds effectively supported the proliferation, differentiation, and myogenesis of C2C12 and bovine satellite cells (Xiang et al., 2022). In another study, the combination of 3% glutenin of pH 3 dissolved in water with 1.5% chitosan at ratio of 1:1 enabled the formation of 3D porous scaffold through water annealing (Wu et al., 2024). The addition of chitosan into glutenin-based scaffolds enhanced structural (pore size, porosity, and swelling), physical (thermal stability, disulfide bonds, secondary structure), and biological (proliferation and differentiation of porcine satellite cells) properties through the increase of -NH₂ and -OH groups (Wu et al., 2024). Consequently, increasing glutenin solubility through pH adjustment or by combining it with other biomaterials can improve processability, thereby enabling the fabrication of scaffolds.

Decellularization of plant-derived materials

Decellularization is the process of removing all cellular components, leaving the tissue structure and ECM (Contessi Negrini et al., 2020; Murugan et al., 2024; Thyden et al., 2022). Decellularized plant sources are ideal biomaterials for scaffolds because of their structural and functional properties that support cell adhesion, proliferation, and differentiation through the vascular system of oxygen and nutrients (Chen et al., 2024b; Jones et al., 2023). Furthermore, the edibility and low cost of decellularized plant-derived materials contribute to the production of safe and economical scaffolds for cultured meat. However, the structural and functional properties of decellularized plant scaffolds exhibit significant variability depending on the plant source (Chen et al., 2024b). Previous studies have explored the potential of various decellularized plant materials, including parsley, spinach, and banana leaves, as scaffold sources. Decellularized parsley scaffolds promote the proliferation and differentiation of C2C12 myoblasts by forming longitudinal and transverse pore structures (Chen et al., 2024b). Similarly, primary bovine satellite cells cultured on decellularized spinach leaves maintain 99% viability and 25% differentiation compared to gelatin-coated glass slides (Jones et al., 2021). Decellularized celery scaffolds support chicken myoblast proliferation and differentiation, with fully grown myoblasts completely covering the scaffold surface and forming fiber-like myotube structures (Hong and Do, 2024). Additionally, various plant-derived sources, including banana leaves, mushrooms, and apples, have been decellularized as scaffolds for cultured meat production (Banavar et al., 2024; Singh et al., 2023; Sood et al., 2024). Therefore, considering biocompatibility, safety, and economic efficiency, the decellularization of plant-derived materials can be an effective biomaterial for cultured meat scaffolds.

Algae-Derived Biomaterials

Algae are a diverse group of photosynthetic organisms that inhabit aquatic environments and have been consumed by humans for centuries (Wells et al., 2017). Algae are considered safe food products that contain abundant bioactive compounds, such as polysaccharides, proteins, bioactive peptides, fatty acids, and vitamins (Diaz et al., 2022). Algae are generally categorized into macroalgae and microalgae based on their size (Wang et al., 2023b). Macroalgae are multicellular organisms classified into three groups: red seaweed (Rhodophyceae), brown seaweed (Phaeophyceae), and green seaweed (Chlorophyceae). In contrast, microalgae are unicellular organisms, consisting of diatoms (Bacillariophyceae), green algae (Chlorophyceae), golden algae (Chrysophyceae), and blue-green algae (Cyanophyceae; Catarina Guedes et al., 2011; Pina-Pérez et al., 2017). Microalgae are rich in proteins, such as essential amino acids and bioactive peptides, whereas macroalgae are primarily composed of polysaccharides (Afonso et al., 2019). Studies have shown that microalgae can be challenging to use as food ingredients in cultured meat scaffolds due to their pigmentation, aquatic odor, and high moisture content, which can negatively impact the texture and taste of the final product (Caporgno et al., 2020; Zhang et al., 2022). Consequently, macroalgae are often considered more suitable biomaterials than microalgae for creating edible scaffolds in cultured meat applications. Table 3 displays the characteristics of algae-derived biomaterials applicable to scaffold fabrication. While carrageenan, alginate, and agarose exhibit excellent gelling and thickening properties, their limited cell-binding sites and low mechanical stability restrict their use in scaffold fabrication. To produce cultured meat, these biomaterials often require combination with other biopolymers.

Carrageenan

Carrageenan, a sulfated polysaccharide extracted from red seaweed, is composed of repeating disaccharide subunits. Carrageenan is classified into six types, *t*-, κ -, λ -, θ -, *v*-, and μ -carrageenan (Qamar et al., 2024). *t*-Carrageenan forms a resilient gel in the presence of calcium salts. However, *t*-carrageenan has a softer gel strength than κ -carrageenan due to the 2-sulfate groups on its exterior forming additional bonds through calcium interactions (Pettinelli et al., 2020). Accordingly, κ -carrageenan is mostly used in the food industry because it can form gels, similar to how natural substances called glycosaminoglycans form gels (Marques et al., 2022). At high temperatures of 75°C–80°C, κ -carrageenan exists as random

Biomaterial	Source	Strength	Limitation	Reference
Carrageenan	Red seaweed	Gel formation, resembles glycosaminoglycans, provides thickening and emulsifying properties, biocompatibility, biodegradability, non- immunogenicity, non-toxicity	High moisture content, low mechanical stability	 Ãlvarez-Viñas et al. (2024); Khrunyk et al. (2020); Marques et al. (2022); Rhein-Knudsen et al. (2015); Zhang et al. (2019)
Alginate	Brown seaweed	Gel formation through interaction with cations	Lack of cellular attachment sites	de Laia et al. (2014); Lee et al. (2024a); Wang et al. (2024c)
Agarose	Red seaweed	Firm and porous gel formation, resembles ECM, support cell growth, high water holding capacity	Lack of cell-binding domains	Garakani et al. (2020); Hong et al. (2024a); Samrot et al. (2023); Sánchez-Salcedo et al. (2008); Zarrintaj et al. (2018)

ECM, extracellular matrix.

coils in solution due to electrostatic repulsion between polymer chains. Upon cooling, these chains undergo a conformational change, forming aggregated helical dimers through intermolecular interactions, ultimately leading to gelation (Rhein-Knudsen et al., 2015). Therefore, κ -carrageenan serves as an effective stabilizer in food products, exhibiting thickening, gelling, and emulsifying properties (Alvarez-Viñas et al., 2024). *k*-Carrageenan has also gained attention as a biomaterial for scaffold fabrication in cultured meat production, due to its biocompatibility, biodegradability, non-immunogenicity, and nontoxicity (Khrunyk et al., 2020). However, the inherent high moisture content of κ-carrageenan-based scaffolds contributes to substantial swelling, consequently resulting in reduced mechanical stability and increased brittleness (Zhang et al., 2019). To effectively utilize κ-carrageenan in scaffold fabrication, its mechanical strength should be improved by forming a double network structure through the incorporation of other biomaterials. A previous study developed an edible hydrogel crosslinked with κ -carrageenan and konjac glucomannan for culturing porcine adipose tissue to produce cultured meat (Gu et al., 2024). Hydrogels fabricated with single k-carrageenan or konjac glucomannan were prone to collapse and rupture, whereas those with κ -carrageenan or konjac glucomannan ratios of 5:5, 4:6, and 3:7 exhibited superior mechanical strength (hardness and chewiness), viscoelasticity, and biocompatibility (cell viability, differentiation, and lipid content; Gu et al., 2024). In another study, Ulagesan et al. (2024) combined κ -carrageenan with sodium alginate to create a bioink for culturing fish muscle satellite cells. A mixture of 6% sodium alginate and 4% K-carrageenan proved optimal for printing, offering enhanced antibacterial and sensory properties (Ulagesan et al., 2024). These studies suggest that k-carrageenan holds promise as a biomaterial for improving the mechanical properties of scaffolds when combined with other biomaterials.

Alginate

Alginate, an anionic polysaccharide derived from brown seaweed, is composed of β -L-guluronic acid (G-form) and α -Dmannuronic acid (M-form) in a linear polymer. Alginate can form net-structured gels through interactions with divalent cations, such as Ba^{2+} , Ca^{2+} , and Sr^{2+} (de Laia et al., 2014; Wang et al., 2024c). However, the use of pure alginate as a scaffold material is limited owing to its lack of cellular attachment sites (Lee et al., 2024a). Recent studies have focused on combining other biomaterials to overcome this limitation. An alginate-cellulose hydrogel, derived from the medulla of Undaria pinnatifida (commonly known as miyeok or sea mustard) improved structural (porosity and microstructure), physical (viscoelasticity and water holding capacity) and biological (cell adhesion, proliferation, and differentiation) properties, compared to that composed of 2% alginate alone (Lee et al., 2024a). Scaffolds composed of 2% sodium alginate and 5% gelatin at a ratio of 2:1 and coated with 0.1% tea polyphenols promoted the adhesion, proliferation, and differentiation of mouse and rabbit myoblasts (Chen et al., 2023a). Since the mechanical properties of the scaffold can be enhanced through electrostatic interactions between the carboxylate moieties of sodium alginate and the protonated amine groups of chitosan, a prior study developed 2% alginate and 2% chitosan containing scaffolds coated with 0.5% collagen and 0.5% gelatin for cultured meat production (Li et al., 2022b). These scaffolds demonstrated good structural (porosity and structural stability), physical (water holding capacity), and biological (cell viability, proliferation, and differentiation) properties (Li et al., 2022b). Interestingly, a previous study demonstrated that alginate fibers fabricated through wet-spinning with 1% sodium alginate and 11% calcium chloride exhibited a positively charged surface (Ben-Arye and Levenberg, 2019; Seo et al., 2023). This positively charged surface significantly enhanced C2C12 myoblast adhesion and viability up to 87.78% and 97.18%, respectively. Overall, these results show that alginate can be a useful material for making scaffolds for cultured meat. This can be achieved by combining alginate with other materials or by changing the way alginate is structured.

Agarose

Agarose is a linear polysaccharide linked by alternating α -1,3 and β -1,4 glycosidic bonds (Samrot et al., 2023). The chemical structure of agarose is similar to that of the ECM, enabling formation of a firm and porous scaffold suitable for cell growth (Garakani et al., 2020; Zarrintaj et al., 2018). Moreover, high water holding capacity of agarose provides sufficient supplies of oxygen and nutrients for the proliferation and differentiation of cells along with its superior biocompatibility (Samrot et al., 2023; Sánchez-Salcedo et al., 2008). However, the absence of cell-binding domains in agarose significantly limits its application as a scaffold biomaterial for cultured meat (Garakani et al., 2020; Hong et al., 2024). This limitation can be addressed by structurally modifying agarose through blending with other biomaterials (Zarrintaj et al., 2018). A previous study demonstrated that crosslinking 2% agarose with 5% soy protein isolate and subsequent coating with 1% gelatin significantly enhanced mechanical strength and structural stability (Hong et al., 2024). This modification resulted in increased water absorption, mechanical strength, cell viability, and adipogenic differentiation. In 0.375% salmon gelatin and 0.375% alginate scaffolds supplemented with 0.1% glycerol, 0.25% agarose also effectively increased the growth of C2C12 myoblasts, along with improvements in microstructure and water interaction capacity (Enrione et al., 2017). Collectively, these studies suggest that the incorporation of other biomaterials to augment cell-binding domains within agarose scaffolds can significantly enhance their suitability for applications in cultured meat production.

Microbial-Derived Biomaterials

Microbial biomaterials are produced via microbial fermentation involving various genera of bacteria, yeast, and molds (Choi and Shin, 2020; Moradi et al., 2021). Polysaccharides are the most widely utilized biomaterials among six major classes: polysaccharides, polynucleotides, polyesters, polythioesters, inorganic polyanhydrides, and polyamides (Choi and Shin, 2020; Nešić et al., 2019). This widespread use of polysaccharides is primarily attributed to their desirable properties, including biodegradability, biocompatibility, and non-toxicity. Bacterial polysaccharides are categorized into cytosolic polysaccharides, lipopolysaccharides, and extracellular polysaccharides. Extracellular polysaccharides are further divided into homopolysaccharides and heteropolysaccharides depending on their monosaccharide composition (Zikmanis et al., 2020). Herein, bacterial cellulose and gellan are representative biomaterials of homopolysaccharides and heteropolysaccharides, respectively (İncili et al., 2025). Table 4 shows the properties of the microbially derived biomaterials used for scaffold fabrication in cultured meat production. Bacterial cellulose and gellan are promising biomaterials for enhancing the mechanical strength of scaffolds. However, low nutritional value of bacterial cellulose and lack of cell-binding site of gellan should be addressed for scaffold applications.

Bacterial cellulose

Bacterial cellulose and plant cellulose share the same molecular composition, both consisting of long chains of glucose molecules. However, bacterial cellulose exhibits a unique 3D hierarchical nanofiber structure (Choi and Shin, 2020). Despite primarily being produced by *Gluconacetobacter* at a laboratory scale, bacterial cellulose exhibits superior properties compared to plant cellulose. These include enhanced mechanical stability, thermostability, crystallinity, and purity (free of lignin, hemicellulose, and pectin; Choi and Shin, 2020; Khan et al., 2022; Tang et al., 2024; Torgbo and Sukyai, 2018). Additionally, it possesses desirable characteristics such as high surface area, permeability, porosity, water-holding capacity, biocompatibility, and biodegradability, enabling its application in diverse fields. However, cellulose-based scaffolds,

Biomaterial	Source	Strength	Limitation	Reference
Bacterial cellulose	Gluconacetobacter	Superior mechanical stability, thermostability, crystallinity, purity, surface area, permeability, porosity, water holding capacity, biodegradability	Low nutritional value due to their indigestible properties	Choi and Shin (2020); Khan et al. (2022); Tang et al. (2024); Torgbo and Sukyai (2018); Wang et al. (2024b)
Gellan	Sphingomonas elodea	Gel formation through cation- mediated helical bonding, low water resistance	Low cell attachment due to the bioinert properties	Alharbi et al. (2024); Chen et al. (2023b); Ferris et al. (2013); İncili et al. (2025); Koivisto et al. (2019); Moxon and Smith (2016)

Table 4. Properties of microbially derived biomaterials for manufacturing scaffolds

primarily composed of dietary fiber, are limited in providing abundant nutritional value due to their indigestible properties (Wang et al., 2024b). In fact, bacterial cellulose has rarely been utilized as a scaffold biomaterial for cultured meat. A previous study reported that while bacterial nanocellulose can potentially support the formation of mature myotubes by providing surface anchor points, C2C12 myoblasts exhibited limited attachment compared to traditional cell culture plastics over a 3-day incubation period (Rybchyn et al., 2021). This finding suggests potential limitations for its application in cultured meat production. However, within the field of tissue engineering, bacterial nanocellulose has demonstrated significant success in culturing human skeletal muscle myoblasts (Mastrodimos et al., 2024). These cultures exhibit a physiologically similar morphology to myofibers and display superior mechanical properties compared to commercially available matrices. These findings suggest that a deeper understanding of bacterial cellulose could open its potential for wider applications in cultured meat.

Gellan

Gellan, an anionic polymeric polysaccharide synthesized by *Sphingomonas elodea*, forms a hydrogel network through cation-mediated helical bonding (Alharbi et al., 2024). During gelation, monovalent cations promote aggregation by suppressing electrostatic repulsions, while divalent cations form direct bridges between pairs of carboxyl groups (Ferris et al., 2013; Moxon and Smith, 2016). Divalent cations, which form stronger gels with gellan than monovalent cations, are primarily used in scaffold fabrication. Conversely, gellan has limited water resistance which makes it suitable for applications as a thickener and gelling agent (Ferris et al., 2013; İncili et al., 2025). Due to its bioinertness and limited cell attachment, gellan is often combined with other biomaterials for scaffold (Koivisto et al., 2019). For example, a previous study successfully addressed the limitations of gellan gum by creating a composite scaffold (Chen et al., 2023b). This scaffold incorporated 1% gellan gum and 0.5% gelatin in a 2:3 ratio and was crosslinked using 0.18 M calcium ions. The results demonstrated significantly improved biocompatibility, including enhanced cell attachment, proliferation, and differentiation of chicken skeletal muscle satellite cells. Additionally, 2% gellan gum was blended with 0.5% and 1% soy or pea protein isolates and these gellan-protein hydrogels exhibited excellent biocompatibility and homogeneous cell encapsulation. Consequently, combining gellan with other biomaterials is crucial to enhance its cell-attachment properties and enable its successful application in scaffold fabrication.

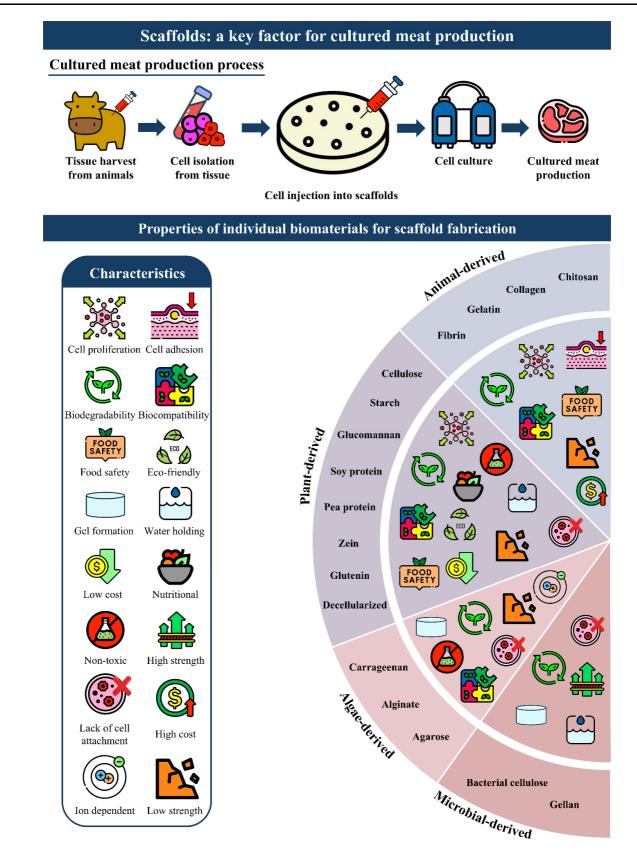


Fig. 1. Properties of individual biomaterials for scaffolds in cultured meat production. This figure comprehensively illustrates the major properties of individual biomaterials for fabricating scaffolds in the production of cultured meat. The advantages and limitations of animal-derived, plant-derived, algae-derived, and microbe-derived biomaterials for scaffold applications are presented with characteristic icons.

Conclusion

The properties of scaffolds, which play a crucial role in determining the structural, functional, and sensory qualities of cultured meat, are influenced by the type of biomaterials. Biomaterials for scaffolds should possess suitable properties such as structural stability, edibility, and biocompatibility to mimic the muscle tissues of meat. This review highlights the strengths and limitations of individual biomaterials depending on biological sources for fabricating ideal scaffolds in cultured meat production (Fig. 1). However, combining one biomaterial with other biomaterials is essential to address the limitations of individual biomaterials. Therefore, further investigation should focus on the fabrication of scaffolds that support cell culture and mimic muscle tissue through the optimization of biomaterial combinations. Furthermore, scaffold fabrication techniques such as freeze-drying, 3D bioprinting, electrospinning, and electrospray should be selected and optimized according to the type of biomaterials. In conclusion, this review comprehensively examines the properties of biomaterials essential for developing ideal scaffolds for cultured meat production. The successful production of cultured meat necessitates the integration of suitable biomaterials with advanced scaffold fabrication techniques.

Conflicts of Interest

The authors declare no potential conflicts of interest.

Acknowledgements

This work was supported by the Korea Institute of Planning and Evaluation for Technology in Food, Agriculture, and Forestry (IPET) through the High Value-added Food Technology Development Program funded by the Ministry of Agriculture, Food, and Rural Affairs (MAFRA) (322006-05-02-CG000) and the National Research Foundation of Korea (NRF) grant funded by the Korea government (MSIT) (No. 2022R1A2C1008327).

Author Contributions

Conceptualization: Park SM, Ryoo JH, Kwon HC, Han SG. Investigation: Park SM, Ryoo JH. Writing - original draft: Park SM, Ryoo JH, Kwon HC. Writing - review & editing: Park SM, Ryoo JH, Kwon HC, Han SG.

Ethics Approval

This article does not require IRB/IACUC approval because there are no human and animal participants.

References

- Abedi E, Pourmohammadi K. 2021. Chemical modifications and their effects on gluten protein: An extensive review. Food Chem 343:128398.
- Afonso NC, Catarino MD, Silva AMS, Cardoso SM. 2019. Brown macroalgae as valuable food ingredients. Antioxidants 8:365.

Ahmad K, Lim JH, Lee EJ, Chun HJ, Ali S, Ahmad SS, Shaikh S, Choi I. 2021. Extracellular matrix and the production of

cultured meat. Foods 10:3116.

- Alharbi HY, Alnoman RB, Aljohani MS, Al-Anazia M, Monier M. 2024. Synthesis and characterization of gellan gum-based hydrogels for drug delivery applications. Int J Biol Macromol 258:128828.
- Alonso-Sande M, Teijeiro-Osorio D, Remuñán-López C, Alonso MJ. 2009. Glucomannan, a promising polysaccharide for biopharmaceutical purposes. Eur J Pharm Biopharm 72:453-462.
- Alvarez-Viñas M, Domínguez H, Torres MD. 2024. Evaluation of carrageenans extracted by an eco-friendly technology as source for gelled matrices with potential food application. Int J Biol Macromol 279:135288.
- Apriyanto A, Compart J, Fettke J. 2022. A review of starch, a unique biopolymer: Structure, metabolism and in *planta* modifications. Plant Sci 318:111223.
- Banavar A, Sarkarat R, Amirvaresi A, Li X, Nguyen C, Kaplan DL, Nitin N, Ovissipour R. 2024. Decellularized banana leaves: Eco-friendly scaffolds for cell-based seafood. Front Sustain Food Syst 8:1341151.
- Başyiğit B, Altun G, Özaslan ZT, Karaaslan M. 2024. Synthesizing mechanically robust natural pea protein hydrogels via deep cryogenic treatment: State of the art in bioactive compound delivery system. Food Hydrocoll 146:109202.

Ben-Arye T, Levenberg S. 2019. Tissue engineering for clean meat production. Front Sustain Food Syst 3:46.

- Bezjak D, Orellana N, Valdés JH, Corrales T, Acevedo CA. 2024. Towards understanding the role of microstructured edible scaffolds for cultured meat production. Food Bioprocess Technol 17:767-779.
- Bhat ZF, Kumar S, Fayaz H. 2015. *In vitro* meat production: Challenges and benefits over conventional meat production. J Integr Agric 14:241-248.
- Bomkamp C, Skaalure SC, Fernando GF, Ben-Arye T, Swartz EW, Specht EA. 2022. Scaffolding biomaterials for 3D cultivated meat: Prospects and challenges. Adv Sci 9:2102908.
- Buléon A, Colonna P, Planchot V, Ball S. 1998. Starch granules: Structure and biosynthesis. Int J Biol Macromol 23:85-112.
- Caporgno MP, Böcker L, Müssner C, Stirnemann E, Haberkorn I, Adelmann H, Handschin S, Windhab EJ, Mathys, A. 2020. Extruded meat analogues based on yellow, heterotrophically cultivated *Auxenochlorella protothecoides* microalgae. Innov Food Sci Emerg Technol 59:102275.
- Catarina Guedes A, Barbosa CR, Amaro HM, Pereira CI, Xavier Malcata F. 2011. Microalgal and cyanobacterial cell extracts for use as natural antibacterial additives against food pathogens. Int J Food Sci Technol 46:862-870.
- Chen X, Li L, Chen L, Shao W, Chen Y, Fan X, Liu Y, Tang C, Ding S, Xu X. 2023a. Tea polyphenols coated sodium alginate-gelatin 3D edible scaffold for cultured meat. Food Res Int 173:113267.
- Chen Y, Li L, Chen L, Shao W, Chen X, Fan X, Liu Y, Ding S, Xu X, Zhou G, Feng X. 2023b. Gellan gum-gelatin scaffolds with Ca²⁺ crosslinking for constructing a structured cell cultured meat model. Biomaterials 299:122176.
- Chen Y, Zhang W, Ding X, Ding S, Tang C, Zeng X, Wang J, Zhou G. 2024a. Programmable scaffolds with aligned porous structures for cell cultured meat. Food Chem 430:137098.
- Chen Z, Xiong W, Guo Y, Jin X, Wang L, Ge C, Tan W, Zhou Y. 2024b. Three-dimensional pore structure of the decellularized parsley scaffold regulates myogenic differentiation for cell cultured meat. J Food Sci 89:5646-5658.
- Chen ZG, Wang PW, Wei B, Mo XM, Cui FZ. 2010. Electrospun collagen–chitosan nanofiber: A biomimetic extracellular matrix for endothelial cell and smooth muscle cell. Acta Biomater 6:372-382.
- Chien KB, Shah RN. 2012. Novel soy protein scaffolds for tissue regeneration: Material characterization and interaction with human mesenchymal stem cells. Acta Biomater 8:694-703.
- Choi SM, Shin EJ. 2020. The nanofication and functionalization of bacterial cellulose and its applications. Nanomaterials

10:406.

- Chriki S, Ellies-Oury MP, Hocquette JF. 2022. Is "cultured meat" a viable alternative to slaughtering animals and a good comprise between animal welfare and human expectations? Anim Front 12:35-42.
- Contessi Negrini N, Toffoletto N, Farè S, Altomare L. 2020. Plant tissues as 3D natural scaffolds for adipose, bone and tendon tissue regeneration. Front Bioeng Biotechnol 8:723.
- Cooper A, Jana S, Bhattarai N, Zhang M. 2010. Aligned chitosan-based nanofibers for enhanced myogenesis. J Mater Chem 20:8904-8911.
- Courtenay JC, Johns MA, Galembeck F, Deneke C, Lanzoni EM, Costa CA, Scott JL, Sharma RI. 2017. Surface modified cellulose scaffolds for tissue engineering. Cellulose 24:253-267.
- David S, Ianovici I, Guterman Ram G, Shaulov Dvir Y, Lavon N, Levenberg S. 2024. Pea protein-rich scaffolds support 3D bovine skeletal muscle formation for cultivated meat application. Adv Sustain Syst 8:2300499.
- Davidenko N, Schuster CF, Bax DV, Raynal N, Farndale RW, Best SM, Cameron RE. 2015. Control of crosslinking for tailoring collagen-based scaffolds stability and mechanics. Acta Biomater 25:131-142.
- de Laia AGS, de Souza Costa Junior E, de Souza Costa H. 2014. A study of sodium alginate and calcium chloride interaction through films for intervertebral disc regeneration uses. 21° CBECIMAT Congresso Brasileiro de Engenharia e Ciência dos Materiais, Cuiabá, Brasil.
- Diaz CJ, Douglas KJ, Kang K, Kolarik AL, Malinovski R, Torres-Tiji Y, Molino JV, Badary A, Mayfield SP. 2022. Developing algae as a sustainable food source. Front Nutr 9:1029841.
- Djisalov M, Knežić T, Podunavac I, Živojević K, Radonic V, Knežević NŽ, Bobrinetskiy I, Gadjanski I. 2021. Cultivating multidisciplinarity: Manufacturing and sensing challenges in cultured meat production. Biology 10:204.
- Enrione J, Blaker JJ, Brown DI, Weinstein-Oppenheimer CR, Pepczynska M, Olguín Y, Sánchez E, Acevedo CA. 2017. Edible scaffolds based on non-mammalian biopolymers for myoblast growth. Materials 10:1404.
- Estevinho BN, Rocha F. 2018. Application of biopolymers in microencapsulation processes. In Biopolymers for food design. Grumezescu AM, Holban Mm (ed). Academic Press, Cambridge, MA, USA. pp 191-222.
- Falsafi SR, Topuz F, Esfandiari Z, Karaca AC, Jafari SM, Rostamabadi H. 2023. Recent trends in the application of protein electrospun fibers for loading food bioactive compounds. Food Chem X 20:100922.
- Fang H, Yu W, Gao B, Niu Y, Yu L. 2024. Preparation of novel double cross-linked hydrogels of dietary fibers and proteins from soybeans as scaffolds for cultured meat. Food Bioprocess Technol 18:1601-1613.
- Ferris CJ, Gilmore KJ, Wallace GG. 2013. Modified gellan gum hydrogels for tissue engineering applications. Soft Matter 9:3705-3711.
- Fiala N. 2008. Meeting the demand: An estimation of potential future greenhouse gas emissions from meat production. Ecol Econ 67:412-419.
- Garakani SS, Khanmohammadi M, Atoufi Z, Kamrava SK, Setayeshmehr M, Alizadeh R, Faghihi F, Bagher Z, Davachi SM, Abbaspourrad A. 2020. Fabrication of chitosan/agarose scaffolds containing extracellular matrix for tissue engineering applications. Int J Biol Macromol 143:533-545.
- Gerbens-Leenes PW, Mekonnen MM, Hoekstra AY. 2013. The water footprint of poultry, pork and beef: A comparative study in different countries and production systems. Water Resour Ind 1–2:25-36.
- Giteru SG, Ali MA, Oey I. 2021. Recent progress in understanding fundamental interactions and applications of zein. Food Hydrocoll 120:106948.

- Gu X, Hua S, Huang Y, Liu S, Wang Y, Zhou M, Shan T. 2024. κ-Carrageenan/konjac glucomannan composite hydrogelbased 3D porcine cultured meat production. Food Hydrocoll 151:109765.
- Guo X, Wang D, He B, Hu L, Jiang G. 2024. 3D bioprinting of cultured meat: A promising avenue of meat production. Food Bioprocess Technol 17:1659-1680.
- Haugh MG, Thorpe SD, Vinardell T, Buckley CT, Kelly DJ. 2012. The application of plastic compression to modulate fibrin hydrogel mechanical properties. J Mech Behav Biomed Mater 16:66-72.
- He X, Lu W, Sun C, Khalesi H, Mata A, Andaleeb R, Fang Y. 2021. Cellulose and cellulose derivatives: Different colloidal states and food-related applications. Carbohydr Polym 255:117334.
- Hong SJ, Kim DH, Ryoo JH, Park SM, Kwon HC, Keum DH, Shin DM, Han SG. 2024. Influence of gelatin on adhesion, proliferation, and adipogenic differentiation of adipose tissue-derived stem cells cultured on soy protein-agarose scaffolds. Foods 13:2247.
- Hong TK, Do JT. 2024. Generation of chicken contractile skeletal muscle structure using decellularized plant scaffolds. ACS Biomater Sci Eng 10:3500-3512.
- Ianovici I, Zagury Y, Redenski I, Lavon N, Levenberg S. 2022. 3D-printable plant protein-enriched scaffolds for cultivated meat development. Biomaterials 284:121487.
- Incili GK, Razavi R, Hayaloğlu AA, Abedinia A, Mirmoeini SS, Moradi M. 2025. Microbial derived biomaterials: Fabrication, processing, and food application. In Sustainable materials for food packaging and preservation: Food security and sustainability. Ghosh T, Priyadarshi R, Roy S (ed). Elsevier, Amsterdam, The Netherlands. pp 55-84.
- Jeong D, Jang G, Jung WK, Park YH, Bae H. 2024. Stretchable zein-coated alginate fiber for aligning muscle cells to artificially produce cultivated meat. npj Sci Food 8:13.
- Jones JD, Rebello AS, Gaudette GR. 2021. Decellularized spinach: An edible scaffold for laboratory-grown meat. Food Biosci 41:100986.
- Jones JD, Thyden R, Perreault LR, Varieur BM, Patmanidis AA, Daley L, Gaudette GR, Dominko T. 2023. Decellularization: Leveraging a tissue engineering technique for food production. ACS Biomater Sci Eng 9:2292-2300.
- Khan S, Ul-Islam M, Ullah MW, Zhu Y, Narayanan KB, Han SS, Park JK. 2022. Fabrication strategies and biomedical applications of three-dimensional bacterial cellulose-based scaffolds: A review. Int J Biol Macromol 209:9-30.
- Khrunyk Y, Lach S, Petrenko I, Ehrlich H. 2020. Progress in modern marine biomaterials research. Mar Drugs 18:589.
- Kim WJ, Kim Y, Ovissipour R, Nitin N. 2024. Plant-based biomaterials as scaffolds for cellular agriculture. Future Foods 10:100468.
- Klemm D, Heublein B, Fink HP, Bohn A. 2005. Cellulose: Fascinating biopolymer and sustainable raw material. Angew Chem Int Ed 44:3358-3393.
- Koivisto JT, Gering C, Karvinen J, Maria Cherian R, Belay B, Hyttinen J, Aalto-Setälä K, Kellomki M, Parraga J. 2019. Mechanically biomimetic gelatin–gellan gum hydrogels for 3D culture of beating human cardiomyocytes. ACS Appl Mater Interfaces 11:20589-20602.
- Kong Y, Ong S, Liu MH, Yu H, Huang D. 2022. Functional composite microbeads for cell-based meat culture: Effect of animal gelatin coating on cell proliferation and differentiation. J Phys D Appl Phys 55:345401.
- Kumar A, Sood A, Han SS. 2023. Technological and structural aspects of scaffold manufacturing for cultured meat: Recent advances, challenges, and opportunities. Crit Rev Food Sci Nutr 63:585-612.
- Lee H, Kim D, Choi KH, Lee S, Jo M, Chun SY, Son Y, Lee JH, Kim K, Lee TB, Keum J, Yoon M, Cha HJ, Rho S, Cho SC,

Lee YS. 2024a. Animal-free scaffold from brown algae provides a three-dimensional cell growth and differentiation environment for steak-like cultivated meat. Food Hydrocoll 152:109944.

- Lee M, Park S, Choi B, Choi W, Lee H, Lee JM, Lee ST, Yoo KH, Han D, Bang G. 2024b. Cultured meat with enriched organoleptic properties by regulating cell differentiation. Nat Commun 15:77.
- Lee M, Park S, Choi B, Kim J, Choi W, Jeong I, Han D, Koh WG, Hong J. 2022. Tailoring a gelatin/agar matrix for the synergistic effect with cells to produce high-quality cultured meat. ACS Appl Mater Interfaces 14:38235-38245.
- Levi S, Yen FC, Baruch L, Machluf M. 2022. Scaffolding technologies for the engineering of cultured meat: Towards a safe, sustainable, and scalable production. Trends Food Sci Technol 126:13-25.
- Li CH, Yang IH, Ke CJ, Chi CY, Matahum J, Kuan CY, Celikkin N, Swieszkowski W, Lin FH. 2022a. The production of fatcontaining cultured meat by stacking aligned muscle layers and adipose layers formed from gelatin-soymilk scaffold. Front Bioeng Biotechnol 10:875069.
- Li L, Chen L, Chen X, Chen Y, Ding S, Fan X, Liu Y, Xu X, Zhou G, Zhu B, Ullah N, Feng X. 2022b. Chitosan-sodium alginate-collagen/gelatin three-dimensional edible scaffolds for building a structured model for cell cultured meat. Int J Biol Macromol 209:668-679.
- Li R, Dai T, Tan Y, Fu G, Wan Y, Liu C, McClements DJ. 2020. Fabrication of pea protein-tannic acid complexes: Impact on formation, stability, and digestion of flaxseed oil emulsions. Food Chem 310:125828.
- Lou H, Lu H, Zhang S, Shi Y, Xu E, Liu D, Chen Q. 2024. Highly aligned myotubes formation of piscine satellite cells in 3D fibrin hydrogels of cultured meat. Int J Biol Macromol 282:136879.
- Lu H, Tian Y. 2021. Nanostarch: Preparation, modification, and application in pickering emulsions. J Agric Food Chem 69:6929-6942.
- Lu H, Ying K, Shi Y, Liu D, Chen Q. 2022. Bioprocessing by decellularized scaffold biomaterials in cultured meat: A review. Bioengineering 9:787.
- Marques DMC, Silva JC, Serro AP, Cabral JMS, Sanjuan-Alberte P, Ferreira FC. 2022. 3D bioprinting of novel κ-carrageenan bioinks: An algae-derived polysaccharide. Bioengineering 9:109.
- Mastrodimos M, Jain S, Badv M, Shen J, Montazerian H, Meyer CE, Annabi N, Weiss PS. 2024. Human skeletal muscle myoblast culture in aligned bacterial nanocellulose and commercial matrices. ACS Appl Mater Interfaces 16:47150-47162.
- Melzener L, Spaans S, Hauck N, Pötgens AJG, Flack JE, Post MJ, Doğan A. 2023. Short-stranded zein fibers for muscle tissue engineering in alginate-based composite hydrogels. Gels 9:914.
- Milani JM, Tirgarian B. 2020. An overview of edible protein-based packaging: Main sources, advantages, drawbacks, recent progressions and food applications. J Packag Technol Res 4:103-115.
- Mohammadian M, Madadlou A. 2018. Technological functionality and biological properties of food protein nanofibrils formed by heating at acidic condition. Trends Food Sci Technol 75:115-128.
- Moradi M, Guimarães JT, Sahin S. 2021. Current applications of exopolysaccharides from lactic acid bacteria in the development of food active edible packaging. Curr Opin Food Sci 40:33-39.
- Moxon SR, Smith AM. 2016. Controlling the rheology of gellan gum hydrogels in cell culture conditions. Int J Biol Macromol 84:79-86.
- Murugan P, Yap WS, Ezhilarasu H, Suntornnond R, Le QB, Singh S, Seah JSH, Tan PL, Zhou W, Tan LP, Choudhury D. 2024. Decellularised plant scaffolds facilitate porcine skeletal muscle tissue engineering for cultivated meat biomanufacturing.

npj Sci Food 8:25.

- Nešić A, Cabrera-Barjas G, Dimitrijević-Branković S, Davidović S, Radovanović N, Delattre C. 2019. Prospect of polysaccharide-based materials as advanced food packaging. Molecules 25:135.
- Ng S, Kurisawa M. 2021. Integrating biomaterials and food biopolymers for cultured meat production. Acta Biomater 124:108-129.
- Niu R, Xin Q, Xu E, Yao S, Chen M, Liu D. 2024. Nanostarch-stimulated cell adhesion in 3D bioprinted hydrogel scaffolds for cell cultured meat. ACS Appl Mater Interfaces 16:23015-23026.
- Park S, Jung S, Heo J, Koh WG, Lee S, Hong J. 2021. Chitosan/cellulose-based porous nanofilm delivering C-phycocyanin: A novel platform for the production of cost-effective cultured meat. ACS Appl Mater Interfaces 13:32193-32204.
- Pettinelli N, Rodríguez-Llamazares S, Bouza R, Barral L, Feijoo-Bandín S, Lago F. 2020. Carrageenan-based physically crosslinked injectable hydrogel for wound healing and tissue repairing applications. Int J Pharm 589:119828.
- Pina-Pérez MC, Rivas A, Martínez A, Rodrigo D. 2017. Antimicrobial potential of macro and microalgae against pathogenic and spoilage microorganisms in food. Food Chem 235:34-44.
- Post MJ, Levenberg S, Kaplan DL, Genovese N, Fu J, Bryant CJ, Negowetti N, Verzijden K, Moutsatsou P. 2020. Scientific, sustainability and regulatory challenges of cultured meat. Nat Food 1:403-415.
- Qamar SA, Junaid M, Riasat A, Jahangeer M, Bilal M, Mu BZ. 2024. Carrageenan-based hybrids with biopolymers and nano-structured materials for biomimetic applications. Starch Stärke 76:2200018.
- Ran X, Lou X, Zheng H, Gu Q, Yang H. 2022. Improving the texture and rheological qualities of a plant-based fishball analogue by using konjac glucomannan to enhance crosslinks with soy protein. Innov Food Sci Emerg Technol 75: 102910.
- Ran X, Yang H. 2022. Promoted strain-hardening and crystallinity of a soy protein-konjac glucomannan complex gel by konjac glucomannan. Food Hydrocoll 133:107959.
- Rao KM, Kim HJ, Won S, Choi SM, Han SS. 2023. Effect of grape seed extract on gelatin-based edible 3D-hydrogels for cultured meat application. Gels 9:65.
- Reiss J, Robertson S, Suzuki M. 2021. Cell sources for cultivated meat: Applications and considerations throughout the production workflow. Int J Mol Sci 22:7513.
- Rhein-Knudsen N, Ale MT, Meyer AS. 2015. Seaweed hydrocolloid production: An update on enzyme assisted extraction and modification technologies. Mar Drugs 13:3340-3359.
- Rojas-Murillo JA, Simental-Mendía MA, Moncada-Saucedo NK, Delgado-Gonzalez P, Islas JF, Roacho-Pérez JA, Garza-Treviño EN. 2022. Physical, mechanical, and biological properties of fibrin scaffolds for cartilage repair. Int J Mol Sci 23:9879.
- Rybchyn MS, Biazik JM, Charlesworth J, le Coutre J. 2021. Nanocellulose from *nata de coco* as a bioscaffold for cell-based meat. ACS Omega 6:33923-33931.
- Samandari M, Saeedinejad F, Quint J, Chuah SXY, Farzad R, Tamayol A. 2023. Repurposing biomedical muscle tissue engineering for cellular agriculture: Challenges and opportunities. Trends Biotechnol 41:887-906.
- Samrot AV, Sathiyasree M, Rahim SBA, Renitta RE, Kasipandian K, Krithika Shree S, Rajalakshmi D, Shobana N, Dhiva S, Abirami S, Visvanathan S, Mohanty BK, Shankar Sabesan G, Chinni SV. 2023. Scaffold using chitosan, agarose, cellulose, dextran and protein for tissue engineering: A review. Polymers 15:1525.
- Sánchez-Salcedo S, Nieto A, Vallet-Regí M. 2008. Hydroxyapatite/ β -tricalcium phosphate/agarose macroporous scaffolds for

bone tissue engineering. Chem Eng J 137:62-71.

- Santos ACA, Camarena DEM, Roncoli Reigado G, Chambergo FS, Nunes VA, Trindade MA, Stuchi Maria-Engler S. 2023. Tissue engineering challenges for cultivated meat to meet the real demand of a global market. Int J Mol Sci 24:6033.
- Santos AEA, Guadalupe JL, Albergaria JDS, Almeida IA, Moreira AMS, Copola AGL, Araújo IP, de Paula AM, Neves BRA, Santos JPF, da Silva AB, Jorge EC, de Oliveira Andrade L. 2024. Random cellulose acetate nanofíbers: A breakthrough for cultivated meat production. Front Nutr 10:1297926.
- Seah JSH, Singh S, Tan LP, Choudhury D. 2022. Scaffolds for the manufacture of cultured meat. Crit Rev Biotechnol 42:311-323.
- Seo JW, Jung WK, Park YH, Bae H. 2023. Development of cultivable alginate fibers for an ideal cell-cultivated meat scaffold and production of hybrid cultured meat. Carbohydr Polym 321:121287.
- Shan G, Xu Z, Jiang L, Zhang Y, Sui X. 2024. Fabrication and characterization of glycerin-plasticized soy protein amyloid fibril scaffolds by unidirectional freeze casting method. Food Hydrocoll 147:109400.
- Shanthakumar P, Klepacka J, Bains A, Chawla P, Dhull SB, Najda A. 2022. The current situation of pea protein and its application in the food industry. Molecules 27:5354.
- Singh A, Singh SK, Kumar V, Gupta J, Kumar M, Sarma DK, Singh S, Kumawat M, Verma V. 2023. Derivation and characterization of novel cytocompatible decellularized tissue scaffold for myoblast growth and differentiation. Cells 13:41.
- Siró I, Plackett D. 2010. Microfibrillated cellulose and new nanocomposite materials: A review. Cellulose 17:459-494.
- Sood A, Singhmar R, Son Y, Jo CH, Choi S, Kumar A, Han SS. 2024. Tuning the efficacy of decellularized apple by coating with alginate/gelatin to behave as a bioscaffold for cultured meat production. Food Res Int 177:113907.
- Stone AK, Karalash A, Tyler RT, Warkentin TD, Nickerson MT. 2015. Functional attributes of pea protein isolates prepared using different extraction methods and cultivars. Food Res Int 76:31-38.
- Sui X, Zhang T, Jiang L. 2021. Soy protein: Molecular structure revisited and recent advances in processing technologies. Annu Rev Food Sci Technol 12:119-147.
- Tan J, Li L, Wang H, Wei L, Gao X, Zeng Z, Liu S, Fan Y, Liu T, Chen J. 2021. Biofunctionalized fibrin gel co-embedded with BMSCs and VEGF for accelerating skin injury repair. Mater Sci Eng 121:111749.
- Tang X, Deng G, Yang L, Wang X, Xiang W, Zou Y, Lu N. 2024. Konjac glucomannan-fibrin composite hydrogel as a model for ideal scaffolds for cell-culture meat. Food Res Int 187:114425.
- Tarafdar A, Gaur VK, Rawat N, Wankhade PR, Gaur GK, Awasthi MK, Sagar NA, Sirohi R. 2021. Advances in biomaterial production from animal derived waste. Bioengineered 12:8247-8258.
- Thyden R, Perreault LR, Jones JD, Notman H, Varieur BM, Patmanidis AA, Dominko T, Gaudette GR. 2022. An edible, decellularized plant derived cell carrier for lab grown meat. Appl Sci 12:5155.
- Tian H, Guo G, Fu X, Yao Y, Yuan L, Xiang A. 2018. Fabrication, properties and applications of soy-protein-based materials: A review. Int J Biol Macromol 120:475-490.
- Torgbo S, Sukyai P. 2018. Bacterial cellulose-based scaffold materials for bone tissue engineering. Appl Mater Today 11:34-49.
- Torres FG, Commeaux S, Troncoso OP. 2013. Starch-based biomaterials for wound-dressing applications. Starch Stärke 65:543-551.
- Tuomisto HL, Teixeira de Mattos MJ. 2011. Environmental impacts of cultured meat production. Environ Sci Technol

45:6117-6123.

- Ulagesan S, Krishnan S, Nam TJ, Choi YH. 2024. Production of fish fillet analogues using novel fish muscle cell powder and sodium alginate-*κ*-carrageenan based bio-ink. Food Hydrocoll 157:110446.
- Ul-Islam M, Alabbosh KF, Manan S, Khan S, Ahmad F, Ullah MW. 2024. Chitosan-based nanostructured biomaterials: Synthesis, properties, and biomedical applications. Adv Ind Eng Polym Res 7:79-99.
- Wang D, Sun J, Li J, Sun Z, Liu F, Du L, Wang D. 2022. Preparation and characterization of gelatin/zein nanofiber films loaded with perillaldehyde, thymol, or ε-polylysine and evaluation of their effects on the preservation of chilled chicken breast. Food Chem 373:131439.
- Wang J, Dai S, Xiang N, Zhang L, Zhong W, Shao P, Feng S. 2024a. Cell-based meat scaffold based on a 3D-printed starchbased gel. J Agric Food Chem 72:19143-19154.
- Wang L, Li G, Li X, Zhang Y, Liu G, Xie M, Zheng Z, Wang X, Chen Y, Kaplan DL. 2024b. Emerging materials in cultivated meat: Engineering sustainable food solutions: A review. Adv Funct Mater 35:2413316.
- Wang M, Zhou J, Tavares J, Pinto CA, Saraiva JA, Prieto MA, Cao H, Xiao J, Simal-Gandara J, Barba FJ. 2023a. Applications of algae to obtain healthier meat products: A critical review on nutrients, acceptability and quality. Crit Rev Food Sci Nutr 63:8357-8374.
- Wang X, Wang M, Xu Y, Yin J, Hu J. 2024c. A 3D-printable gelatin/alginate/ε-poly-l-lysine hydrogel scaffold to enable porcine muscle stem cells expansion and differentiation for cultured meat development. Int J Biol Macromol 271:131980.
- Wang Y, Zhong Z, Munawar N, Wang R, Zan L, Zhu J. 2024d. Production of green-natural and "authentic" cultured meat based on proanthocyanidins-dialdehyde chitosan-collagen ternary hybrid edible scaffolds. Food Res Int 175:113757.
- Wang Y, Zhong Z, Munawar N, Zan L, Zhu J. 2024e. 3D edible scaffolds with yeast protein: A novel alternative protein scaffold for the production of high-quality cell-cultured meat. Int J Biol Macromol 259:129134.
- Wang Y, Zou L, Liu W, Chen X. 2023b. An overview of recent progress in engineering three-dimensional scaffolds for cultured meat production. Foods 12:2614.
- Wei Z, Dai S, Huang J, Hu X, Ge C, Zhang X, Yang K, Shao P, Sun P, Xiang N. 2023. Soy protein amyloid fibril scaffold for cultivated meat application. ACS Appl Mater Interfaces 15:15108-15119.
- Wells ML, Potin P, Craigie JS, Raven JA, Merchant SS, Helliwell KE, Smith AG, Camire ME, Brawley SH. 2017. Algae as nutritional and functional food sources: Revisiting our understanding. J Appl Phycol 29:949-982.
- Wieser H. 2007. Chemistry of gluten proteins. Food Microbiol 24:115-119.
- Wu X, Han W, Hou L, Lin D, Li J, Lin S, Yang J, Liao L, Zeng X. 2024. Glutenin-chitosan 3D porous scaffolds with tunable stiffness and systematized microstructure for cultured meat model. Int J Biol Macromol 267:131438.
- Xiang N, Yuen Jr. JSK, Stout AJ, Rubio NR, Chen Y, Kaplan DL. 2022. 3D porous scaffolds from wheat glutenin for cultured meat applications. Biomaterials 285:121543.
- Xiao C, Gao S, Wang H, Zhang L. 2000a. Blend films from chitosan and konjac glucomannan solutions. J Appl Polym Sci 76:509-515.
- Xiao C, Gao S, Zhang L. 2000b. Blend films from konjac glucomannan and sodium alginate solutions and their preservative effect. J Appl Polym Sci 77:617-626.
- Xie X, Bu T, Zhu Q, Ma L, Gao Z, Du T, Liu S, Wang J. 2024. Chitosan-puerarin composite hydrogel with magnetic enhanced photothermal properties as sustained antimicrobial coatings for beef preservation. Int J Biol Macromol 278:135027.

- Xing Q, Yates K, Vogt C, Qian Z, Frost MC, Zhao F. 2014. Increasing mechanical strength of gelatin hydrogels by divalent metal ion removal. Sci Rep 4:4706.
- Xu H, Cai S, Sellers A, Yang Y. 2014. Electrospun ultrafine fibrous wheat glutenin scaffolds with three-dimensionally random organization and water stability for soft tissue engineering. J Biotechnol 184:179-186.
- Yao Y, Yuen Jr. JSK, Sylvia R, Fennelly C, Cera L, Zhang KL, Li C, Kaplan DL. 2024. Cultivated meat from aligned muscle layers and adipose layers formed from glutenin films. ACS Biomater Sci Eng 10:814-824.
- Ye S, Zongo AWS, Shah BR, Li J, Li B. 2021. Konjac glucomannan (kgm), deacetylated kgm (da-kgm), and degraded kgm derivatives: A special focus on colloidal nutrition. J Agric Food Chem 69:12921-12932.
- Zarrintaj P, Manouchehri S, Ahmadi Z, Saeb MR, Urbanska AM, Kaplan DL, Mozafari M. 2018. Agarose-based biomaterials for tissue engineering. Carbohydr Polym 187:66-84.
- Zernov A, Baruch L, Machluf M. 2022. Chitosan-collagen hydrogel microparticles as edible cell microcarriers for cultured meat. Food Hydrocoll 129:107632.
- Zhang AQ, Li XY, Liu BH, Yin YQ, Zhang HL, Zhang YH. 2023. Comprehensive application possibility: Construction hydrophilic, amphiphilic and hydrophobic system of modified zein by enzymatic or cysteine modification. Food Hydrocoll 135:108159.
- Zhang C, Guan X, Yu S, Zhou J, Chen J. 2022. Production of meat alternatives using live cells, cultures and plant proteins. Curr Opin Food Sci 43:43-52.
- Zhang Y, Zhou D, Chen J, Zhang X, Li X, Zhao W, Xu T. 2019. Biomaterials based on marine resources for 3D bioprinting applications. Mar Drugs 17:555.
- Zheng YY, Chen Y, Zhu HZ, Li CB, Song WJ, Ding SJ, Zhou GH. 2022a. Production of cultured meat by culturing porcine smooth muscle cells *in vitro* with food grade peanut wire-drawing protein scaffold. Food Res Int 159:111561.
- Zheng YY, Shi YF, Zhu HZ, Ding SJ, Zhou GH. 2022b. Quality evaluation of cultured meat with plant protein scaffold. Food Res Int 161:111818.
- Zhuang K, Shu X, Xie W. 2024. Konjac glucomannan-based composite materials: Construction, biomedical applications, and prospects. Carbohydr Polym 344:122503.
- Zikmanis P, Kolesovs S, Semjonovs P. 2020. Production of biodegradable microbial polymers from whey. Bioresour Bioprocess 7:36.